

REPORT DOCUMENTATION PAGE

Form Approved

OMB No 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)

2. REPORT DATE

25-2-94

3. REPORT TYPE AND DATES COVERED

Technical Report

4. TITLE AND SUBTITLE

Silicone Grease as a Precursor to a Pseudo Crown-Ether
Ligand: Crystal Structure of
[K⁺]₃[K(Me₂SiO)₇⁺][HIn(CH₂CMe₃)₃]₄⁻

5. FUNDING NUMBERS

Grant:

N00014-90-J-1530

R&T Code:

4135002

6. AUTHOR(S)

Melvyn Rowen Churchill, Charles H. Lake, Sun-Hua L. Chao
and O. T. Beachley, Jr.

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)

Department of Chemistry
State University of New York at Buffalo
Buffalo, NY 14214-3094

8. PERFORMING ORGANIZATION
REPORT NUMBER

Technical Report
No. 38

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)

Office of Naval Research
800 N. Quincy Street
Arlington, VA 22217-5000

10. SPONSORING/MONITORING
AGENCY REPORT NUMBER

n/a

11. SUPPLEMENTARY NOTES

Accepted for publication - Organometallics

12a. DISTRIBUTION/AVAILABILITY STATEMENT

This document has been approved for public release and
sale; its distribution is unlimited. Reproduction in
whole or in part is permitted for any purpose of the
United States government.

12b. DISTRIBUTION CODE

n/a

13. ABSTRACT (Maximum 200 words)

The crystallization of K[(HIn(CH₂CMe₃)₃] from heptane in the presence of
silicone grease led to the formation of the title compound, in which one potassium
cation is surrounded by a planar cyclo-(Me₂SiO)₇ ligand; K⁺...O distances range
from 2.86(3) to 2.99(4)Å.

DTIC
ELECTE
MAR 04 1994
S B D

14. SUBJECT TERMS

Indium-hydride, silicon-oxygen crown ether, X-ray structural
study

15. NUMBER OF PAGES

11

16. PRICE CODE

n/a

17. SECURITY CLASSIFICATION
OF REPORT

Unclassified

18. SECURITY CLASSIFICATION
OF THIS PAGE

Unclassified

19. SECURITY CLASSIFICATION
OF ABSTRACT

Unclassified

20. LIMITATION OF ABSTRACT

UL

NSN 7540-01-280-5500

Standard Form 298 (Rev 2-89)
Prescribed by ANSI Std Z39-18
298-102

AD-A276 343



94-07072

14p

94 3 13 117

OFFICE OF NAVAL RESEARCH

Contract N-00014-90-J-1530

R&T Code 4135002

TECHNICAL REPORT NO. 38

Silicone Grease as a Precursor to a
Pseudo Crown-Ether Ligand: Crystal Structure of
 $[K^+]_3[K(Me_2SiO)_7]^+ [HIn(CH_2CMe_3)_3]^-$

by

Melvyn Rowen Churchill, Charles H. Lake, Sun-Hua L. Chao
and O. T. Beachley, Jr.

Prepared for Publication

in

Organometallics

State University of New York at Buffalo
Department of Chemistry
Buffalo, New York 14214

25 February 1994

DTIC QUALITY INSPECTED 8

Reproduction in whole or in part is permitted for
any purpose of the United States Government

*This document has been approved for public release
and sale; its distribution is unlimited

Submitted to J. Chem. Soc., Chem. Commun.

Silicone Grease as a Precursor to a Pseudo
Crown-Ether Ligand: Crystal Structure
of $[K^+]_3[K(Me_2SiO)_7^+][HIn(CH_2CMe_3)_3^-]_4$

Melvyn Rowen Churchill, Charles H. Lake, Sun-Hua L. Chao and O. T. Beachley, Jr.

Department of Chemistry, Acheson Hall,

State University of New York at Buffalo

Buffalo, New York 14214, U. S. A.

Summary. The crystallization of $K[HIn(CH_2CMe_3)_3]$ from heptane in the presence of silicone grease led to the formation of the title compound, in which one potassium cation is surrounded by a planar cyclo- $(Me_2SiO)_7$ ligand; $K^+ \cdots O$ distances range from 2.86(3) to 2.99(4) Å.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

We have previously reported the preparation of $\text{K}^+[\text{HIn}(\text{CH}_2\text{CMe}_3)_3]^-$ along with a crystallographic study of the related dinuclear species $\text{K}^+[\text{H}\{\text{In}(\text{CH}_2\text{CMe}_3)_3\}_2]^-$.¹ Attempts to crystallize $\text{K}^+[\text{HIn}(\text{CH}_2\text{CMe}_3)_3]^-$ from pentane at low temperature produced large, colourless, transparent, rectangular crystals in the mother liquor. When the pentane was removed, the crystals became opaque and shattered. In an attempt to protect the material from solvent loss, the following crystallization procedure was used. A sample of $\text{K}^+[\text{HIn}(\text{CH}_2\text{CMe}_3)_3]^-$ and a small amount of Dow Corning[®] high-vacuum silicone grease (intended to protect any crystals thus grown) were placed in a tube equipped with a Solv-Seal joint. Heptane was added by vacuum distillation. The solid dissolved as the mixture was warmed from -196°C to room temperature over 2h. Needle shaped single crystals formed overnight. The crystal used for the X-ray crystallographic study was cut from a larger crystal and mounted in a thin-walled capillary tube. [N. B. All materials were handled under purified argon or in vacuo. Organoindium hydrides are extremely air- and moisture sensitive.]

The completed X-ray diffraction study[†] shows the crystals to have the composition $[\text{K}^+]_3[\text{K}(\text{Me}_2\text{SiO})_7]^+[\text{HIn}(\text{CH}_2\text{CMe}_3)_3]^-_4$. The overall structure is shown in Figure 1. The "bare" potassium cations are associated with the cavity between the $\text{HIn}(\text{CH}_2\text{CMe}_3)_3^-$ ions and interact with hydrogen atoms on various neopentyl groups.

The totally unexpected feature of the structure is the presence of the $(\text{Me}_2\text{SiO})_7$ moiety, which acts as a pseudo crown-ether ligand around atom K(1). Although the structure as a whole is of poor quality, all features of this system are unequivocal. The

(Me_2SiO)₇ moiety is based upon an essentially planar 14-membered Si_7O_7 ring of approximate D_{7h} symmetry. The potassium ion, defined by K(1), is coplanar with this ring and interacts with all seven oxygen atoms of the cyclopolsiloxane ($\text{K}^+ \cdots \text{O} = 2.86(3) - 2.99(4)\text{\AA}$, average = 2.93\AA). Silicon-oxygen distances are $1.54(4) - 1.67(4)\text{\AA}$ (average = 1.61\AA) and silicon-carbon distances are $1.78(7) - 1.99(12)\text{\AA}$ (average = 1.88\AA).

Cyclopolydimethylsiloxanes, (Me_2SiO)_n have been known for some time. The physical properties of the trimer up to the octamer were described about fifty years ago.² Individual species up to at least the tetracontamer ($n = 40$) have since been isolated.³ An electron diffraction study⁴ showed that the trimer, (Me_2SiO)₃, had a planar six-membered ring.⁴ An X-ray diffraction study⁵ of the tetramer, (Me_2SiO)₄, and a partial X-ray diffraction study⁶ of the octamer, (Me_2SiO)₈, showed them to have puckered rings. Electron diffraction studies on the tetramer, pentamer and hexamer⁷ also indicated puckered (SiO)_n rings. Infra-red and Raman spectra of both liquid and solid (Me_2SiO)₇ suggests that each contains a number of conformers;⁸ this, too, suggests a puckered ring. The D_{7h} symmetry exhibited by the (Me_2SiO)₇ ligand in the present structural study is clearly a result of its coordination to the potassium cation.

A search of Chemical Abstracts and secondary review sources⁹ (at the behest of a referee) revealed no other example of a cyclopolsiloxane behaving as a crown ether. Indeed, a paper entitled (in translation) 'Study of the possibility of using cyclodimethylsiloxanes as "crown compounds" ' showed that neither (Me_2SiO)₇ nor (Me_2SiO)₈ was efficacious as a crown ligand toward the Na^+ cation.¹⁰

The derived structure leads to some interesting questions.

(1) Why is the heptameric cyclopolysiloxane, $(\text{Me}_2\text{SiO})_7$, specifically found in the crystals? It seems probable that it is formed by reaction of silicone grease with $[\text{K}^+][\text{HIn}(\text{CH}_2\text{CMe}_3)_3^-]$. Silicone grease consists principally of polydimethylsiloxane ($> 80\%$), dimethylcyclsiloxane ($< 1\%$, ring size unknown) and hydroxy terminated dimethylsiloxane ($\sim 5-10\%$).¹¹ The cyclic heptamer is not even a specifically identified component of silicone grease.

(2) Is it possible to isolate different sized cyclic oligomers, $(\text{Me}_2\text{SiO})_n$, from silicone grease based upon the size of the cation (M^+) in $\text{M}^+[\text{HIn}(\text{CH}_2\text{CMe}_3)_3^-]$?

(3) Can various $(\text{Me}_2\text{SiO})_n$ species be widely used as crown ether ligands?

Finally, the results shown herewithin indicate that silicone grease cannot always be considered as an innocuous inert material, but can participate as a reactant.

Further work is in progress, including a structural study on a triclinic crystal modification of the present structure.

Acknowledgements.

This work was supported, in part, by the Office of Naval Research. Purchase of a Siemens R3m/V diffractometer was made possible by Grant 89-13733 from the Chemical Instrumentation Program of the National Science Foundation.

References

1. O. T. Beachley, Jr., S.-H. L. Chao, M. R. Churchill and R. F. See, Organometallics, 1992, **11**, 1486.
2. M. J. Hunter, J. F. Hyde, E. L. Warrick and H. J. Fletcher, J. Amer. Chem. Soc., 1946, **68**, 667.

See also: J. F. Hyde and R. C. Delong, J. Amer. Chem. Soc., 1941, **63**, 1194;
W. Patnode and D. F. Wilcock, J. Amer. Chem. Soc., 1946, **68**, 358.
3. T. Alvik and J. Dale, Acta Chem. Scand., 1971, **25**, 2131 and references therein.
4. E. H. Aggarwal and S. H. Bauer, J. Chem. Phys., 1950, **18**, 42.
5. H. Steinfink, B. Post, and I. Fankuchen, Acta Cryst., 1955, **8**, 420.
6. L. K. Frevel and M. J. Hunter, J. Amer. Chem. Soc., 1945, **67**, 2275.
7. H. Oberhammer, W. Zeil and G. Fogarasi, J. Mol. Struct., 1973, **18**, 309.
8. T. Alvik and J. Dale, Acta Chem. Scand., 1971, **25**, 2142.
9. (a) G. Wilkinson, F. G. A. Stone, and E. W. Abel, "Comprehensive Organometallic Chemistry", Pergamon Press, 1982, Volume 2, Section 9.1.15.4.2. Cyclosiloxanes, pp 162-163.

(b) E. Lukevics, O. Pudova and R. Sturkovich, "Molecular Structure of Organosilicon Compounds", Ellis Horwood Limited, Chichester, 1989, Section 3.6.1.3. Siloxanes, pp 191-208.

(c) "Organometallic Compounds of Silicon", Ed. D. R. M. Walton, Chapman and Hall, 1985.

10. Yu. A. Yuzhelevskii, V. V. Pchelintsev and N. N. Fedoseeva, Vysokomol. Soedin., Ser. B 1976, 18, 873-4. (Chem. Abstr. 1977, 86, 73181v).
11. Personal communication to O. T. Beachley, Jr. from Cindy Fox (Dow Corning Corporation, Midland, Michigan, 48686 U. S. A.).

Footnote

† Crystal data: $C_{74}H_{178}In_4K_4O_7Si_7$, colourless, $M = 1992.5$, monoclinic, $P2_1/n$; $a = 14.704(2)$, $b = 24.195(3)$, $c = 32.759(6)\text{\AA}$, $\beta = 93.674(12)^\circ$, $V = 11631(3)\text{\AA}^3$, $Z = 4$, $T = 298\text{K}$, $D_c = 1.138\text{ g cm}^{-3}$, $\mu(\text{Mo-K}\alpha) = 1.02\text{ mm}^{-1}$, $F(000) = 4192$. Of 16437 data collected ($2\theta = 5\text{--}45^\circ$), 15243 were independent, but only 3191 were observed ($6\sigma F_o$). Data were corrected for absorption. The data set is extremely weak (average value of $I/\sigma(I)$ is 5.29) and there is disorder in certain of the neopentyl ligands. Final $R = 9.85\%$.

Atomic coordinates, bond lengths and angles and thermal parameters have been deposited at the Cambridge Crystallographic Data Centre. See Notice to Authors, Issue No. 1.

FIGURE CAPTIONS:

Figure 1. Overall structure of $[K^+]_3[K(Me_2SiO)_7^+][HIn(CH_2CMe_3)_3^-]_4$. The hydride ligands attached to indium are shown in calculated positions.

Figure 2. The $K(Me_2SiO)_7^+$ moiety.

Distances of interest (Å) are as follows:

$K(1) \cdots O(1) = 2.99(4)$, $K(1) \cdots O(2) = 2.94(5)$

$K(1) \cdots O(3) = 2.93(3)$, $K(1) \cdots O(4) = 2.93(4)$,

$K(1) \cdots O(5) = 2.86(3)$, $K(1) \cdots O(6) = 2.94(3)$,

$K(1) \cdots O(7) = 2.94(4)$.

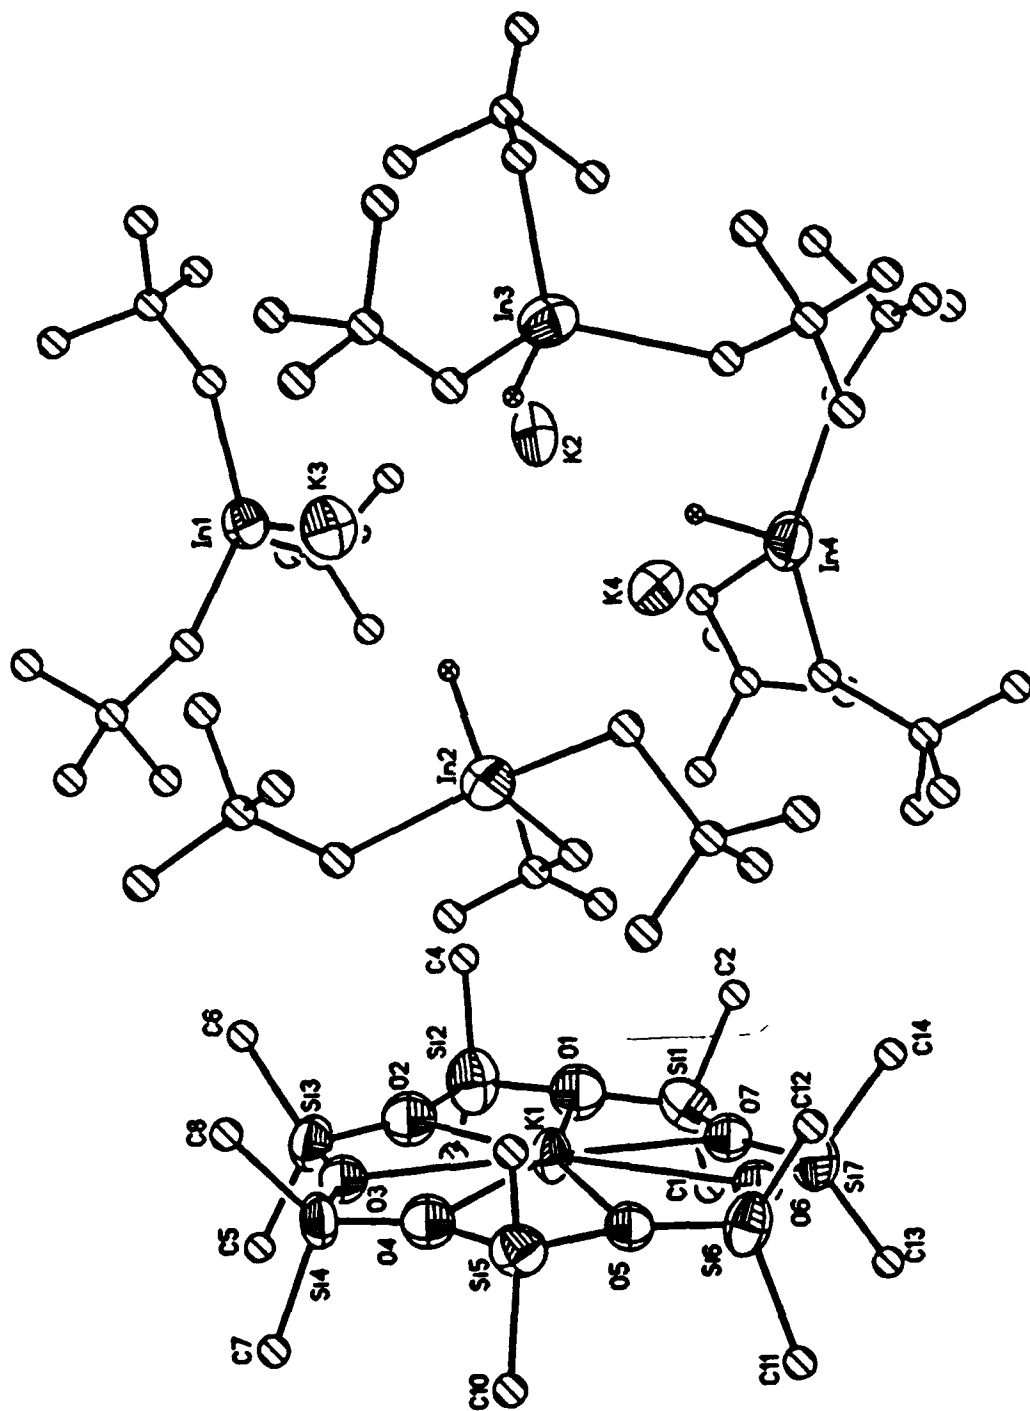


Fig 1

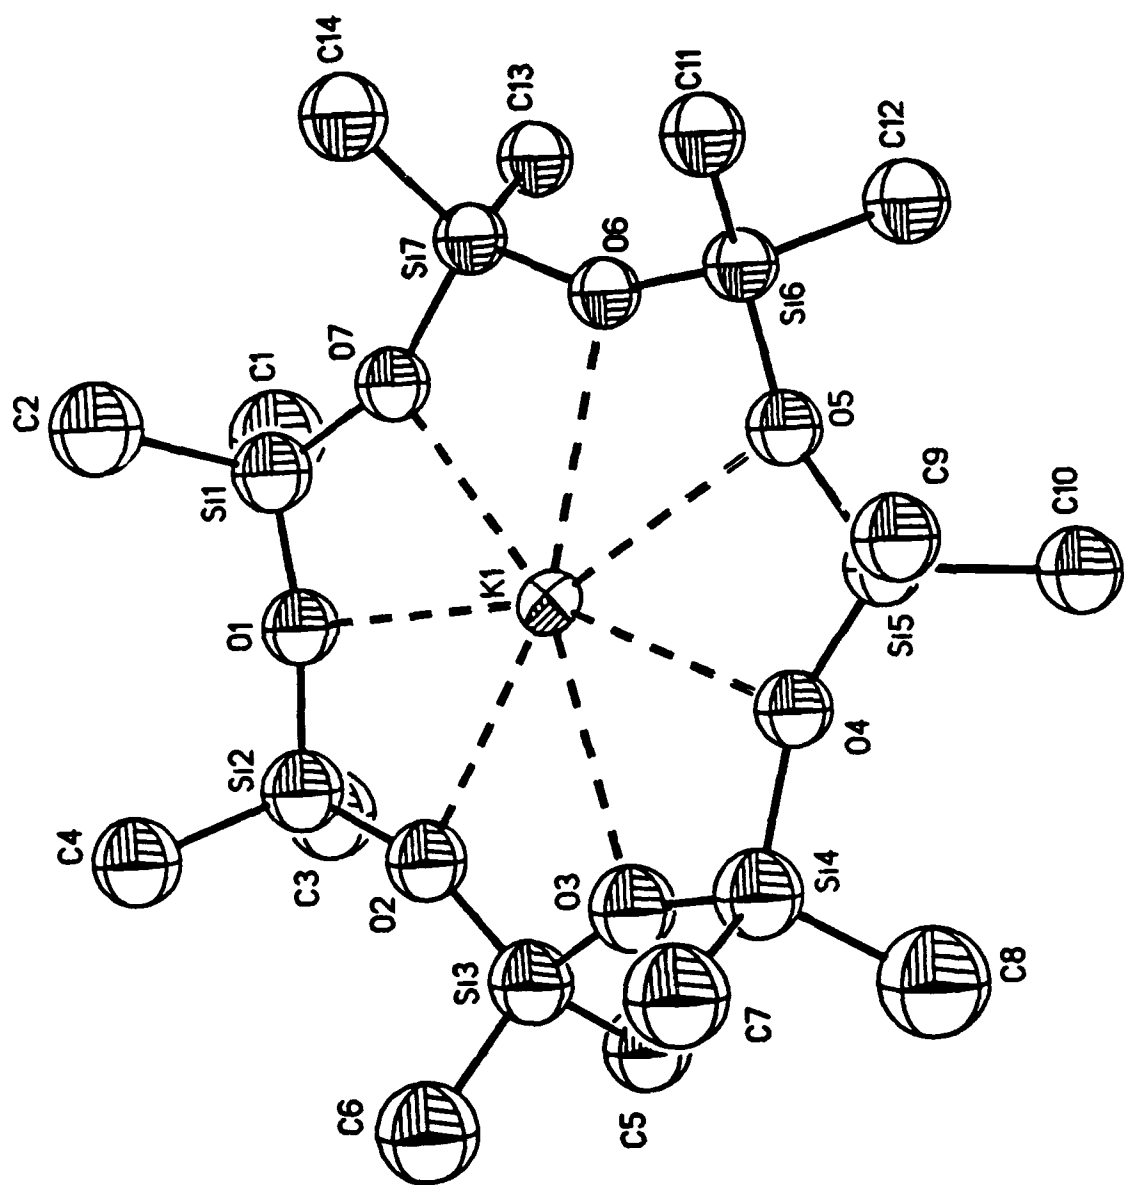


Fig 2

TECHNICAL REPORT DISTRIBUTION LIST - GENERAL

Office of Naval Research (2)*
Chemistry Division, Code 1113
800 North Quincy Street
Arlington, Virginia 22217-5000

Dr. James S. Murday (1)
Chemistry Division, Code 6100
Naval Research Laboratory
Washington, D.C. 20375-5000

Dr. Robert Green, Director (1)
Chemistry Division, Code 385
Naval Air Weapons Center
Weapons Division
China Lake, CA 93555-6001

Dr. Elek Lindner (1)
Naval Command, Control and Ocean
Surveillance Center
RDT&E Division
San Diego, CA 92152-5000

Dr. Bernard E. Douda (1)
Crane Division
Naval Surface Warfare Center
Crane, Indiana 47522-5000

Dr. Richard W. Drisko (1)
Naval Civil Engineering
Laboratory
Code L52
Port Hueneme, CA 93043

Dr. Harold H. Singerman (1)
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Dr. Eugene C. Fischer (1)
Code 2840
Naval Surface Warfare Center
Carderock Division Detachment
Annapolis, MD 21402-1198

Defense Technical Information
Center (2)
Building 5, Cameron Station
Alexandria, VA 22314

* Number of copies to forward